



Designation: D1415 – 18

Standard Test Method for Rubber Property—International Hardness¹

This standard is issued under the fixed designation D1415; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ε) indicates an editorial change since the last revision or reapproval.

This standard has been approved for use by agencies of the U.S. Department of Defense.

1. Scope

1.1 This test method covers a procedure for measuring the hardness of vulcanized or thermoplastic rubber. The hardness is obtained by the difference in penetration depth of a specified dimension ball under two conditions of contact with the rubber: (1) with a small initial force and (2) with a much larger final force. The differential penetration is taken at a specified time and converted to a hardness scale value.

1.2 This test method is technically similar to ISO 48.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.4 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

2. Referenced Documents

2.1 *ASTM Standards:*²

D1349 Practice for Rubber—Standard Conditions for Testing
D2240 Test Method for Rubber Property—Durometer Hardness

D4483 Practice for Evaluating Precision for Test Method Standards in the Rubber and Carbon Black Manufacturing Industries

¹ This test method is under the jurisdiction of ASTM Committee D11 on Rubber and Rubber-like Materials and is the direct responsibility of Subcommittee D11.10 on Physical Testing.

Current edition approved June 1, 2018. Published September 2018. Originally approved in 1956. Last previous edition approved in 2012 as D1415 – 06 (2012). DOI: 10.1520/D1415-18.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

2.2 *International Standard:*³

ISO 48 Rubber, Vulcanized or Thermoplastic — Determination of Hardness (Hardness between 10 and 100 IRHD)

3. Summary of Test Methods

3.1 Four procedures are given to accommodate specimens of different dimensions hardness of vulcanized or thermoplastic rubbers on flat surfaces:

Type S1 and S2, Standard hardness tests; M, Type Micro-hardness tests;
Type L, Low hardness test;
Type H, High hardness test.

3.1.1 *Types S1 and S2 (refer to Table 1)*—The standard test for hardness is the appropriate method for specimens having a thickness described in Section 6, and is appropriate for those having a hardness of 35 IRHD to 85 IRHD. It may be used for those in the range of 30 IRHD to 95 IRHD.

NOTE 1—The hardness values obtained by Types S and S1, within the ranges of 85 IRHD to 95 IRHD and 30 IRHD to 35 IRHD may not agree with those obtained using Types H or L. The differences are not generally considered significant.

3.1.2 *Type M (refer to Table 1)*—The micro-hardness test is a scaled-down version of Type S1 and S2, which permit testing of thinner and smaller specimens. It is applicable for specimens having a thickness described in Section 6, and a hardness of 35 IRHD to 85 IRHD. It may be used for those in the range of 30 IRHD to 95 IRHD.

NOTE 2—The hardness values obtained by Type M may not agree with those obtained using Types S1 or S2 due to the effects of surface variations or specimen configuration.

3.1.3 *Type L*—The appropriate method for specimens having a thickness described in Section 6, and a hardness of 10 IRHD to 35 IRHD.

3.1.4 *Type H*—The appropriate method for specimens having a thickness described in Section 6, and a hardness of 85 IRHD to 100 IRHD.

3.2 In all procedures, the hardness in International Rubber Hardness Degrees (IRHD) is derived from the difference in

³ Available from American National Standards Institute (ANSI), 25 W. 43rd St., 4th Floor, New York, NY 10036.



TABLE 1 Apparatus Requirements

NOTE 1—In Type M micro-hardness testing using instruments in which the test piece table is pressed upwards by a spring, the value of the force on foot is that acting during the period of application of the total indenting force. Before the indenting force increment of 0.145 N is applied, the force on the foot is greater by this amount, and hence is 0.38 ± 0.03 N.

	Type S1	Type S2	Type M	Type L	Type H
Diameter of ball, mm	2.38 ± 0.01	2.50 ± 0.01	0.395 ± 0.005	5.0 ± 0.01	1.0 ± 0.01
Minor force on ball, N ^A	0.30 ± 0.02	0.29 ± 0.02	0.0083 ± 0.0005	0.3 ± 0.02	0.3 ± 0.02
Major force on ball, N ^A	5.23 ± 0.01	5.4 ± 0.01	0.1455 ± 0.0005	5.4 ± 0.01	5.4 ± 0.01
Total force on ball, N ^A	5.53 ± 0.03	5.7 ± 0.03	0.153 ± 0.001	5.7 ± 0.03	5.7 ± 0.03
Outside diameter of foot, mm	20 ± 1	20 ± 1	3.35 ± 0.15	22 ± 1.0	20 ± 1.0
Inside diameter of foot, mm	6 ± 1	6 ± 1	1.00 ± 0.15	10 ± 1.0	6 ± 1.0
Force on foot, N ^B	8.3 ± 1.5	8.3 ± 1.5	0.235 ± 0.03 ^C	8.3 ± 1.5	8.3 ± 1.5

^A Includes frictional forces in apparatus.

^B The force should be adjusted within these limits to the actual area of the foot so that the pressure in the specimen is 30 ± 0.5 kPa.

^C Force on foot during application of total force on ball; force on foot during application of minor force on ball, 0.2 N minimum, 0.4 N maximum.

penetrations and a table or graph constructed from the table. In the micro-tester procedure, the difference in penetration must first be multiplied by scale factor 6. Alternatively, the penetration measuring instrument may be calibrated directly in IRHD.

4. Significance and Use

4.1 The International Hardness test is based on measurement of the penetration of a rigid ball into the rubber specimen under specified conditions. The measured penetration is converted into IRHD, the scale of degrees being so chosen that 0 represents a material having an elastic modulus of zero, and 100 represents a material of infinite elastic modulus.

4.1.1 The scale also fulfills the following conditions over most of the normal range of hardness: one IRHD range represents approximately the same proportionate difference in Young's modulus, and for rubber vulcanizates in the usual range of resilience, readings in IRHD are comparable with those given by a Type A durometer (Test Method D2240) when testing standard specimens.

4.1.1.1 The term "usual range of resilience" is used to exclude those compounds that have unusually high rates of stress relaxation or deformational hysteresis. For such compounds, differences in the dwell time in the two hardness tests (Test Methods D2240 and D1415) result in differences in hardness values. Readings may not be comparable when testing curved or irregularly shaped test specimens.

4.1.2 For substantially elastic isotropic materials like well-vulcanized natural rubbers, the hardness in IRHD bears a known relation to Young's modulus, although for markedly plastic or anisotropic rubbers the relationship will be less precisely known.

4.1.3 The relation between the difference of penetration and the hardness expressed in IRHD is based on the following:

4.1.3.1 The relation⁴ between penetration and Young's modulus for a perfectly elastic isotropic material:

$$D \approx 61.5 R^{2/0.48} \sim F/E^{0.74} \approx f/E^{0.74} \quad (1)$$

⁴ This relation is approximate and is included as an indication.

where:

D = known relationship for a perfectly elastic isotropic material, between indentation,

R = radius of the ball, mm,

F = total indenting force,

E = Young's modulus expressed in megapascals, and

f = contact force

4.1.3.2 Use of a probit (integrated normal error) curve to relate $\log_{10} M$ and hardness in IRHD, as shown in Fig. 1. This curve is defined as follows:

4.1.3.3 The value of $\log_{10} M$ corresponding to the midpoint of the curve is equal to 0.364, that is, $M = 2.31$ MPa or 335 psi.

4.1.3.4 The maximum slope is equal to 57 IRHD per unit increase in $\log_{10} M$.

5. Apparatus

5.1 The essential parts of the apparatus are as follows, the appropriate dimensions and loads being given in Table 1:

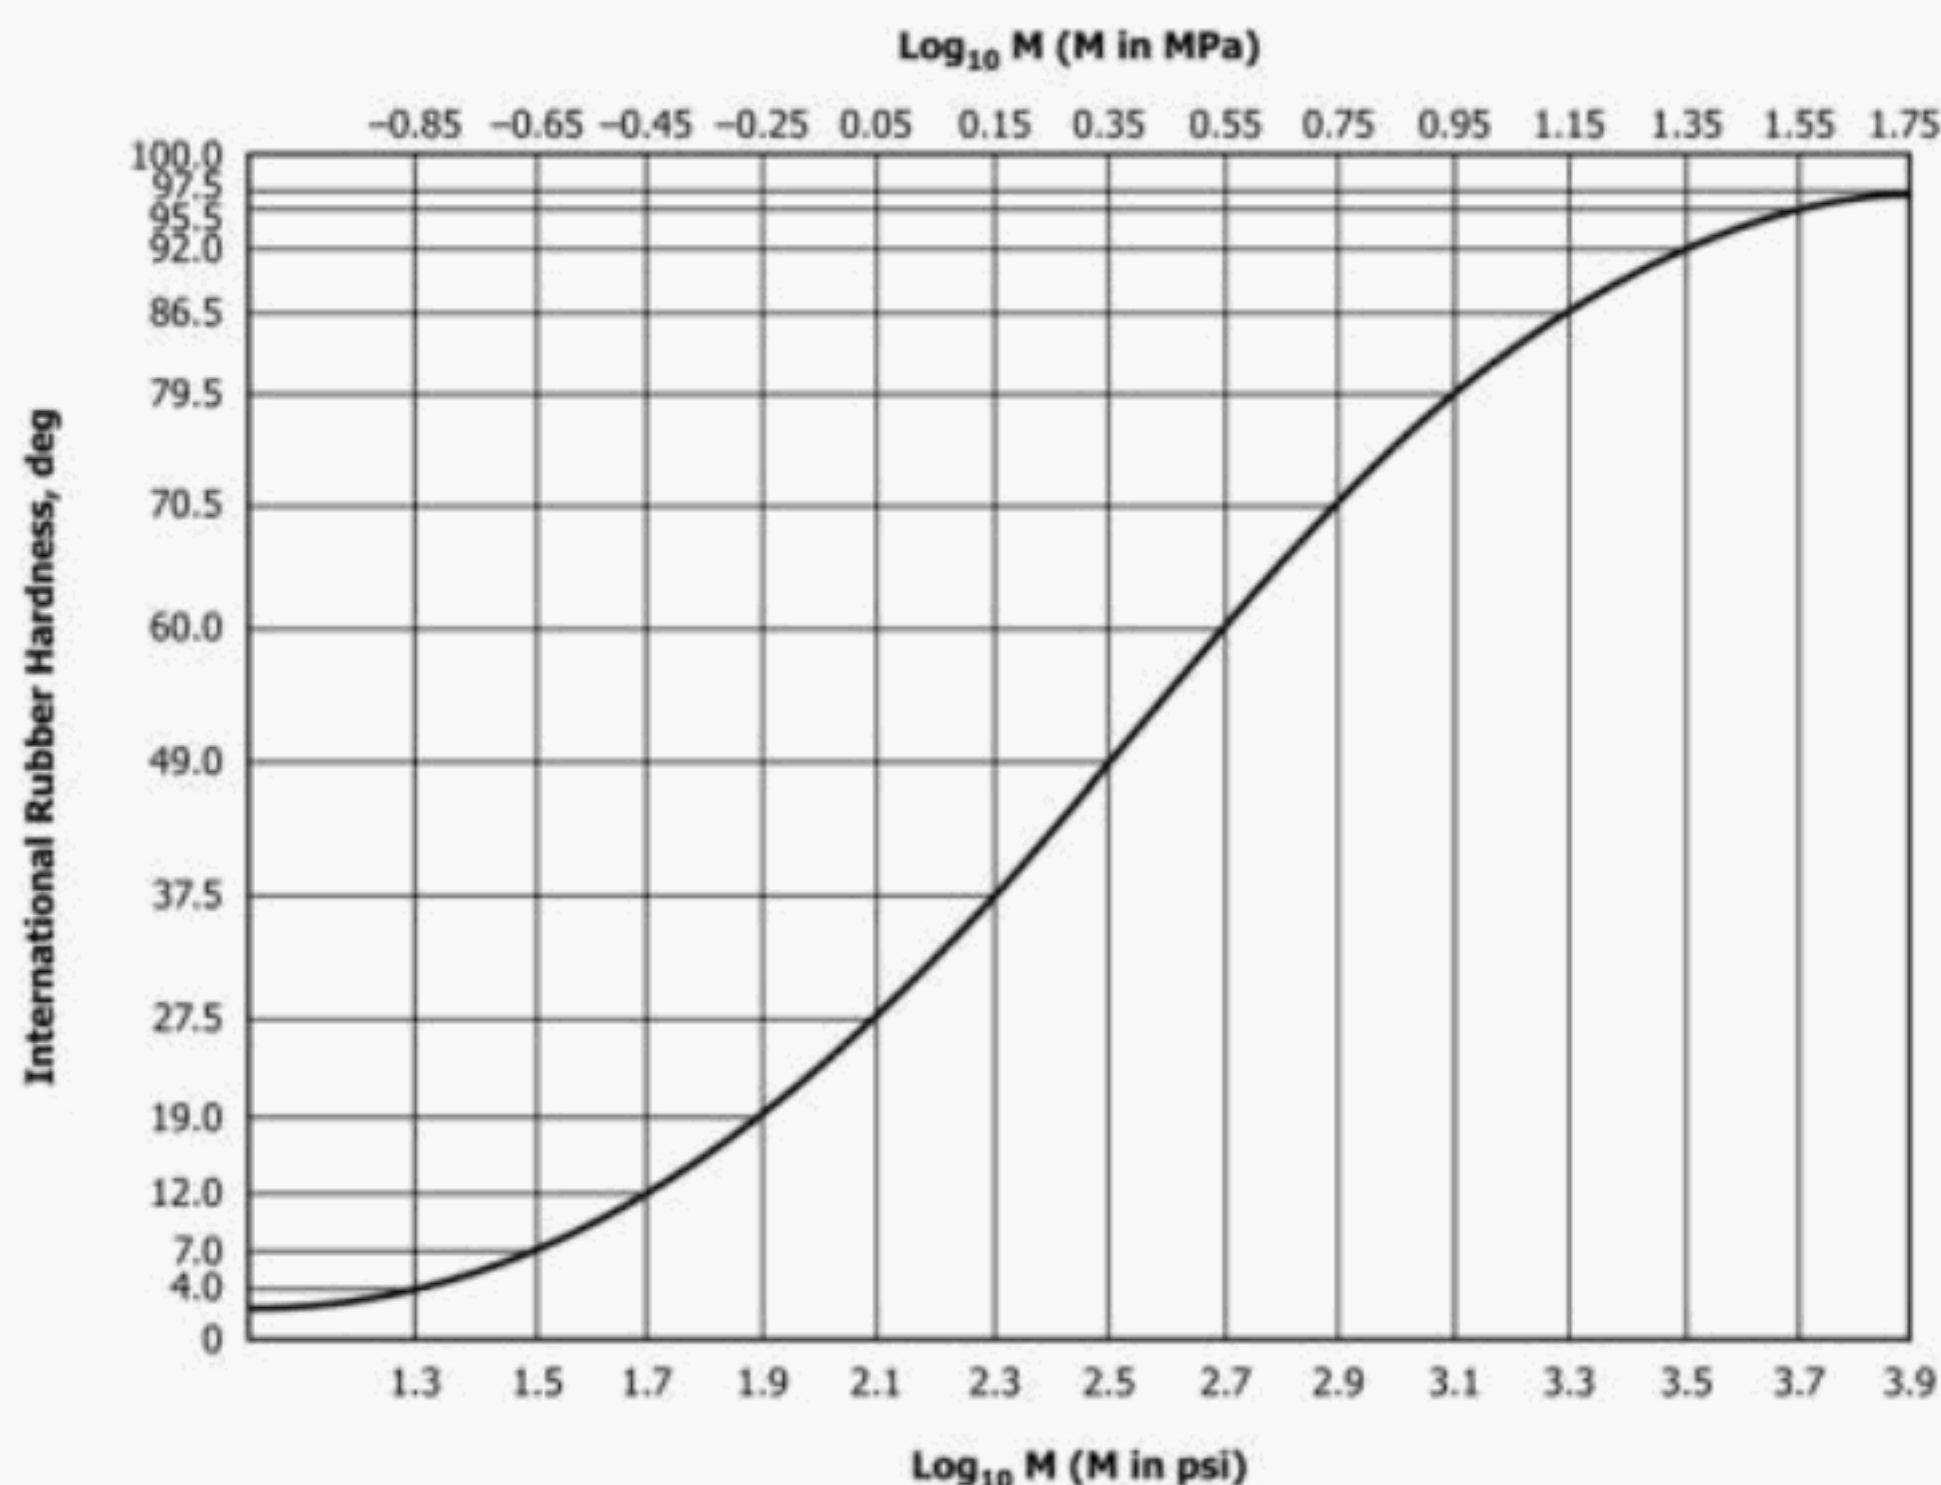
5.1.1 *Vertical Plunger*, terminating in a rigid ball.

5.1.2 *Force Applicator*, for applying a minor force and a major force to the ball, the mass of the plunger, and of any fittings attached to it, and the force of any spring acting on it shall be included in determining the minor and major forces. This is in order that the forces actually applied to the ball shall be as specified.

5.1.3 *Measuring Device*—A mechanical, optical, or electrical device graduated either in standard units of length or in IRHD for measuring the increase in depth of penetration of the plunger caused by the major load.

5.1.4 *Foot*—A flat annular-shaped foot that is rigidly fastened to the penetration-measuring device and normal to the axis of the plunger, and which during the test is forced against the specimen in order to determine accurately the position of the upper surface.

5.1.5 *Vibrating Device*—For example, an electrically operated buzzer, for gently vibrating the apparatus to overcome any slight friction; this should not exceed 5 % of the minor load. This device may be omitted on apparatus without any friction.

FIG. 1 Point Curve to Relate $\text{Log}_{10} M$ and the Hardness in IRHD

6. Test Specimen

6.1 Tests intended to be comparable must be made on specimens of the same thickness that have smooth, flat, and parallel upper and lower surfaces. Up to three specimens may be plied to obtain the required thickness. The dimensions of the specimen depend on the test type being used to measure the hardness.

6.2 *Types S1 and S2*—The Types S1 and S2 specimens shall be between 8 and 10 mm in thickness. Nonstandard specimens may be either thicker or thinner but in no case less than 2 mm thick. The lateral dimensions of both standard and nonstandard specimens shall be such that no test is made at a distance from the edge of the specimen less than the appropriate distance shown in [Table 2](#).

6.3 *Type M*—The Type M specimen micro-hardness tests shall be 2.6 to 0.5 mm in thickness. Nonstandard specimens may be either thicker or thinner but in no case less than 1 mm thick. The lateral dimensions of both standard and nonstandard specimens shall be such that no test is made at a distance from the edge of less than 2 mm. When specimens thicker than 4 mm

are tested on the micro tester because lateral dimensions or area of flatness do not permit testing on a standard tester, the test shall be made at a distance from the edge as great as possible. Curved specimens, for example, O-rings, may be tested with the micro-hardness tester if the specimens are mounted in such a manner as to prevent movement during the test, but the values obtained may not be comparable to those obtained with flat specimens.

6.4 *Type L*—The Type L specimens shall be 10 to 15 mm in thickness. Standard specimens may be either thicker or thinner but in no case less than 2 mm. Nonstandard specimens may be either thicker or thinner but in no case less than 6 mm. The lateral dimensions of both standard and nonstandard specimens shall be such that no test is made at a distance from the edge of the specimen less than the appropriate distance shown in [Table 2](#).

6.5 *Type H*—Refer to [6.2](#) (Types S1 and S2).

7. Test Temperature

7.1 The test shall be normally carried out at 23 ± 2°C (73.4 ± 3.6°F). The specimens shall be maintained at the test temperature for at least 3 h immediately prior to testing. Specimens that are sensitive to atmospheric moisture shall be conditioned in an atmosphere controlled to 50 ± 5 % relative humidity (RH%) for at least 24 h. When tests are made at higher or lower temperatures, the specimens shall be maintained at the conditions of test for a period of time sufficient to reach temperature equilibrium with the testing chamber, and

the temperatures shall be chosen from those specified in Practice [D1349](#), or as otherwise agreed upon between customer and supplier.

TABLE 2 Minimum Distance from Edge of Specimen at Which Test is Made (All types except M)

Total Thickness of Specimen		Minimum Distance from Edge	
mm	in.	mm	in.
4	0.16	7.0	0.28
6	0.25	8.0	0.31
8	0.3	9.0	0.35
10	0.4	10.0	0.40
15	0.6	11.5	0.45
25	1.0	13.0	0.50

TABLE 3 a Conversion of Values of *D* to Type S1, S2, and M IRHD

NOTE 1—*D* = differential indentation, given in inches.

NOTE 2—For Type M, divide *D* by 6.

NOTE 3—Inch to Type S1 and S2 millimeter: multiply *D* by 25.4; for Type M, divide that result by 6.

Movement of Plunger <i>D</i> (in)	IRHD	Movement of Plunger <i>D</i> (in)	IRHD	Movement of Plunger <i>D</i> (in)	IRHD	Movement of Plunger <i>D</i> (in)	IRHD
0.0000	100	0.0133	81	0.0264	62	0.0469	43
0.0024	99	0.0139	80	0.0272	61	0.0483	42
0.0033	98	0.0145	79	0.0281	60	0.0498	41
0.0040	97	0.0151	78	0.0289	59	0.0514	40
0.0047	96	0.0157	77	0.0298	58	0.0530	39
0.0053	95	0.0163	76	0.0308	57	0.0547	38
0.0059	94	0.0170	75	0.0317	56	0.0564	37
0.0065	93	0.0176	74	0.0327	55	0.0581	36
0.0071	92	0.0183	73	0.0337	54	0.0601	35
0.0077	91	0.0189	72	0.0347	53	0.0621	34
0.0082	90	0.0196	71	0.0358	52	0.0642	33
0.0088	89	0.0203	70	0.0368	51	0.0664	32
0.0093	88	0.0210	69	0.0380	50	0.0686	31
0.0099	87	0.0217	68	0.0391	49	0.0710	30
0.0105	86	0.0225	67	0.0403	48	0.0735	29
0.0110	85	0.0232	66	0.0415	47	0.0761	28
0.0116	84	0.0240	65	0.0428	46		
0.0122	83	0.0247	64	0.0441	45		
0.0127	82	0.0255	63	0.0455	44		

8. Procedure

8.1 Condition the specimen in accordance with 7.1. Slightly dust the upper and lower surfaces of the test specimen with talc. Support the specimen on a horizontal rigid surface, and lower the foot to rest on the surface of the specimen. Press the plunger, with the minor force on the indenting ball, vertically onto the specimen for 5 s.

8.2 If the gauge is graduated directly in IRHD, turn the bezel of the gauge so that the pointer indicates 100 (exercise care to avoid exerting any vertical pressure on the gauge). Add the major force to the plunger and maintain the total force on the ball for 30 s (Note 3). Record the reading on the gauge as the hardness in IRHD.

NOTE 3—During the loading periods, the apparatus shall be gently vibrated to overcome any friction.

8.3 If the measuring device is graduated in inch units, record the movement of the plunger caused by application of the major load for 30 s. If the Type M micro-hardness tester is used, refer to the notes in Table 3a. Convert the value obtained into IRHD by using Table 3a or a graph constructed therefrom.

8.4 If the measuring device is graduated in metric units, the differential indentation, *D*, (in millimeters) of the plunger caused by the additional indenting force (the major load) for 30 s, shall be noted. If the Type M micro-hardness tester is used, refer to Table 3c, as given in Table 3b for Types S1 and S2, Table 3d for Type H, and Table 3e for Type L. Convert the value obtained into IRHD by using Table 3a–Table 3e or a graph constructed therefrom.

8.5 Make one measurement at each of three or five different points distributed evenly over the specimen. Take the median of these measurements rounded to the nearest displayed unit of

IRHD (whole numbers for analog instruments and 0.1 units for digital instruments, if so equipped), and record the result as the hardness value.

9. Report

9.1 Report the following information:

9.1.1 Hardness expressed in IRHD. Values from curved or irregularly shaped specimens shall be quoted as apparent hardness,

9.1.2 Dimensions of the specimen, if a singular entity; the number of pieces, that is, one, two, or three; and their individual dimensions when plied. In the case of curved or irregularly shaped specimens: specimen description, method of mounting, and method of applying test,

9.1.3 Type of surface tested, that is, molded, buffed, or otherwise,

9.1.4 Type of tester used, that is, Type S1, S2, Type M, Type H, or Type L,

9.1.5 Date, time, RH%, and temperature of test, and 9.1.6

Pertinent details that would be deemed important to future replication of the test or as agreed upon between customer and supplier.

10. Precision and Bias⁵

10.1 This precision and bias section has been prepared in accordance with Practice D4483. Refer to this practice for terminology and other statistical calculation details.

10.2 *Precision*—A Type 1 (interlaboratory) test program to determine precision was evaluated in 1981. Both repeatability

⁵ Supporting data have been filed at ASTM International Headquarters and may be obtained by requesting Research Report RR:D11-1024.

TABLE 3 b Conversion of Values of *D* to Types S1 and S2 IRHD (continued)NOTE 1—Types S1 and S2 (*D* = differential indentation with a 2.38 or 2.5 mm Ø indenter, given in mm).

Movement of Plunger <i>D</i> (mm)	IRHD	Movement of Plunger <i>D</i> (mm)	IRHD	Movement of Plunger <i>D</i> (mm)	IRHD	Movement of Plunger <i>D</i> (mm)	IRHD
0.00	100.0	0.46	73.3	0.92	51.6	1.38	38.2
0.01	100.0	0.47	72.7	0.93	51.2	1.39	38.0
0.02	99.9	0.48	72.2	0.94	50.9	1.40	37.8
0.03	99.8	0.49	71.6	0.95	50.5	1.41	37.5
0.04	99.6	0.50	71.0	0.96	50.2	1.42	37.3
0.05	99.3	0.51	70.4	0.97	49.8	1.43	37.1
0.06	99.0	0.52	69.8	0.98	49.5	1.44	36.9
0.07	98.6	0.53	69.3	0.99	49.1	1.45	36.7
0.08	98.1	0.54	68.7	1.00	48.8	1.46	36.5
0.09	97.7	0.55	68.2	1.01	48.5	1.47	36.2
0.10	97.1	0.56	67.6	1.02	48.1	1.48	36.0
0.11	96.5	0.57	67.1	1.03	47.8	1.49	35.8
0.12	95.9	0.58	66.6	1.04	47.5	1.50	35.6
0.13	95.3	0.59	66.0	1.05	47.1	1.51	35.4
0.14	94.7	0.60	65.5	1.06	46.8	1.52	35.2
0.15	94.0	0.61	65.0	1.07	46.5	1.53	35.0
0.16	93.4	0.62	64.5	1.08	46.2	1.54	34.8
0.17	92.7	0.63	64.0	1.09	45.9	1.55	34.6
0.18	92.0	0.64	63.5	1.10	45.6	1.56	34.4
0.19	91.3	0.65	63.0	1.11	45.3	1.57	34.2
0.39	77.6	0.85	54.2	1.31	39.9	1.77	30.5
0.40	77.0	0.86	53.8	1.32	39.6	1.78	30.4
0.41	76.4	0.87	53.4	1.33	39.4	1.79	30.2
0.42	75.8	0.88	53.0	1.34	39.1	1.80	30.0
0.43	75.2	0.89	52.7	1.35	38.9		
0.44	74.5	0.90	52.3	1.36	38.7		
0.45	73.9	0.91	52.0	1.37	38.4		

TABLE 3 c Conversion of Values of *D* to Type M IRHD (continued)NOTE 1—Type M (*D* = differential indentation with a 0.395 mm Ø indenter, given in mm).

Movement of Plunger <i>D</i> (mm)	IRHD	Movement of Plunger <i>D</i> (mm)	IRHD	Movement of Plunger <i>D</i> (mm)	IRHD	Movement of Plunger <i>D</i> (mm)	IRHD
0.000	100.0	0.077	73.3	0.153	51.6	0.230	38.2
0.002	100.0	0.078	72.7	0.155	51.2	0.232	38.0
0.003	99.9	0.080	72.2	0.157	50.9	0.233	37.8
0.005	99.8	0.082	71.6	0.158	50.5	0.235	37.5
0.007	99.6	0.083	71.0	0.160	50.2	0.237	37.3
0.008	99.3	0.085	70.4	0.162	49.8	0.238	37.1
0.010	99.0	0.087	69.8	0.163	49.5	0.240	36.9
0.012	98.6	0.088	69.3	0.165	49.1	0.242	36.7
0.013	98.1	0.090	68.7	0.167	48.8	0.243	36.5
0.015	97.7	0.092	68.2	0.168	48.5	0.245	36.2
0.017	97.1	0.093	67.6	0.170	48.1	0.247	36.0
0.018	96.5	0.095	67.1	0.172	47.8	0.248	35.8
0.020	95.9	0.097	66.6	0.173	47.5	0.250	35.6
0.022	95.3	0.098	66.0	0.175	47.1	0.252	35.4
0.023	94.7	0.100	65.5	0.177	46.8	0.253	35.2
0.025	94.0	0.102	65.0	0.178	46.5	0.255	35.0
0.027	93.4	0.103	64.5	0.180	46.2	0.257	34.8
0.028	92.7	0.105	64.0	0.182	45.9	0.258	34.6
0.030	92.0	0.107	63.5	0.183	45.6	0.260	34.4
0.032	91.3	0.108	63.0	0.185	45.3	0.262	34.2
0.065	77.6	0.142	54.2	0.218	39.9	0.295	30.5
0.067	77.0	0.143	53.8	0.220	39.6	0.297	30.4
0.068	76.4	0.145	53.4	0.222	39.4	0.298	30.2
0.070	75.8	0.147	53.0	0.223	39.1	0.300	30.0
0.072	75.2	0.148	52.7	0.225	38.9		
0.073	74.5	0.150	52.3	0.227	38.7		
0.075	73.9	0.152	52.0	0.228	38.4		

and reproducibility are short term. A period of a few days separates replicate test results. A test result is the median value,

as specified by this test method, obtained on five determinations or measurements of hardness.

TABLE 3 d Conversion of Values of *D* to Type H IRHD (continued)NOTE 1—Type H (*D* = differential indentation with a 1.0 mm Ø indenter, given in mm).

Movement of Plunger <i>D</i> (mm)	IRHD	Movement of Plunger <i>D</i> (mm)	IRHD	Movement of Plunger <i>D</i> (mm)	IRHD
0.00	100.0	0.15	97.3	0.30	91.1
0.01	100.0	0.16	97.0	0.31	90.7
0.02	100.0	0.17	96.6	0.32	90.2
0.03	99.9	0.18	96.2	0.33	89.7
0.04	99.9	0.19	95.8	0.34	89.3
0.05	99.8	0.20	95.4	0.35	88.8
0.06	99.6	0.21	95.0	0.36	88.4
0.07	99.5	0.22	94.6	0.37	87.9
0.08	99.3	0.23	94.2	0.38	87.5
0.09	99.1	0.24	93.8	0.39	87.0
0.10	98.8	0.25	93.4	0.40	86.6
0.11	98.6	0.26	92.9	0.41	86.1
0.12	98.3	0.27	92.5	0.42	85.7
0.13	98.0	0.28	92.0	0.43	85.3
0.14	97.6	0.29	91.6	0.44	84.8

TABLE 3 e Conversion of Values of *D* to Type L IRHD (continued)NOTE 1—Type L (*D* = differential indentation with a 5.0 mm Ø indenter, given in mm).

Movement of Plunger <i>D</i> (mm)	IRHD	Movement of Plunger <i>D</i> (mm)	IRHD	Movement of Plunger <i>D</i> (mm)	IRHD
1.10	34.9	1.80	21.3	2.50	14.1
1.12	34.4	1.82	21.1	2.52	14.0
1.14	33.9	1.84	20.8	2.54	13.8
1.16	33.4	1.86	20.6	2.56	13.7
1.18	32.9	1.88	20.3	2.58	13.5
1.20	32.4	1.90	20.1	2.60	13.4
1.22	31.9	1.92	19.8	2.62	13.3
1.24	31.4	1.94	19.6	2.64	13.1
1.26	30.9	1.96	19.4	2.66	13.0
1.28	30.4	1.98	19.2	2.68	12.8
1.30	30.0	2.00	18.9	2.70	12.7
1.32	29.6	2.02	18.7	2.72	12.6
1.34	29.2	2.04	18.5	2.74	12.5
1.36	28.8	2.06	18.3	2.76	12.3
1.38	28.4	2.08	18.0	2.78	12.2
1.40	28.0	2.10	17.8	2.80	12.1
1.42	27.6	2.12	17.6	2.82	12.0
1.44	27.2	2.14	17.4	2.84	11.8
1.46	26.8	2.16	17.2	2.86	11.7
1.48	26.4	2.18	17.0	2.88	11.6
1.50	26.1	2.20	16.8	2.90	11.5
1.52	25.7	2.22	16.6	2.92	11.4
1.54	25.4	2.24	16.4	2.94	11.3
1.56	25.0	2.26	16.2	2.96	11.2
1.58	24.7	2.28	16.0	2.98	11.1
1.60	24.4	2.30	15.8	3.00	11.0
1.62	24.1	2.32	15.6	3.02	10.9
1.64	23.8	2.34	15.4	3.04	10.8
1.66	23.5	2.36	15.3	3.06	10.6
1.68	23.1	2.38	15.1	3.08	10.5
1.70	22.8	2.40	14.9	3.10	10.4
1.72	22.5	2.42	14.8	3.12	10.3
1.74	22.2	2.44	14.6	3.14	10.2
1.76	21.9	2.46	14.4	3.16	10.1
1.78	21.6	2.48	14.3	3.18	10.0

10.3 Four different materials were used in the interlaboratory program. These were tested in six laboratories on two different days. The results of the precision calculations for repeatability and reproducibility are given in Table 4, in ascending order of material average or level, for each of the materials evaluated.

10.4 The precision of this test method may be expressed in the format of the following statements, which use an appropri-

ate value of *r* or *R*, that is, that value to be used in decisions about test results (obtained with the test method). The appropriate value is that value of *r* or *R* associated with a mean level in Table 4 closest to the mean level under consideration at any given time for any given material in routine testing operations.

10.5 *Repeatability*—The repeatability, *r*, of this test method has been established as the appropriate value tabulated in Table 4. Two single test results, obtained under normal test

TABLE 4 Type 1 Precision Results (IRHD)

Material	Average	Within Laboratory ^A			Between Laboratory ^A		
		S_r	r	$(r)^B$	S_R	R	$(R)^B$
Material 1	41.51	0.1140	0.3227	0.777	3.1126	8.8087	21.221
Material 2	52.67	0.4143	1.1725	2.226	2.7121	7.6752	14.573
Material 3	65.09	0.3617	1.0236	1.573	2.8652	8.1086	12.457
Material 4	75.08	0.5236	1.4818	1.974	2.8091	7.9497	10.589
Pooled values ^C	58.59	0.3915	1.1079	1.891	2.9055	8.2225	14.035

^A S_r = repeatability standard deviation.

r = repeatability = 2.83 times the square root of the repeatability variance.

(r) = repeatability (as a percent of material average).

S_R = reproducibility standard deviation.

R = reproducibility = 2.83 times the square root of the reproducibility variance. (R)

= reproducibility (as a percent of material average).

^B Because the hardness scale is not a linear scale, use caution in interpreting (r) and (R) . No

^C values omitted.

procedures, that differ by more than this tabulated r (for any given level) must be considered as derived from different or nonidentical sample populations.

10.6 Reproducibility—The reproducibility, R , of this test method has been established as the appropriate value tabulated in **Table 4**. Two single test results obtained in two different laboratories, under normal test procedures, that differ by more than the tabulated R (for any given level) must be considered to have come from different or nonidentical sample populations.

10.7 Repeatability and reproducibility expressed as a percentage of the mean level, (r) and (R) , have equivalent

application statements as above for r and R . For the (r) and (R) statements, the difference in the two single test results is expressed as a percent of the arithmetic mean of the two test results.

10.8 Bias—In test method terminology, bias is the difference between an average test value and the reference (or true) test property value. Reference values do not exist for this test method since the value (of the test property) is exclusively defined by the test method. Bias, therefore, cannot be determined.

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; <http://www.copyright.com/>